

# **Recommended Practice for Materials and Fabrication of 1¼Cr-½Mo Steel Pressure Vessels for Service above 825 °F (440 °C)**

API RECOMMENDED PRACTICE 934-E  
SECOND EDITION, JANUARY 2018



AMERICAN PETROLEUM INSTITUTE

## Special Notes

API publications necessarily address problems of a general nature. With respect to particular circumstances, local, state, and federal laws and regulations should be reviewed.

Neither API nor any of API's employees, subcontractors, consultants, committees, or other assignees make any warranty or representation, either express or implied, with respect to the accuracy, completeness, or usefulness of the information contained herein, or assume any liability or responsibility for any use, or the results of such use, of any information or process disclosed in this publication. Neither API nor any of API's employees, subcontractors, consultants, or other assignees represent that use of this publication would not infringe upon privately owned rights.

API publications may be used by anyone desiring to do so. Every effort has been made by the Institute to assure the accuracy and reliability of the data contained in them; however, the Institute makes no representation, warranty, or guarantee in connection with this publication and hereby expressly disclaims any liability or responsibility for loss or damage resulting from its use or for the violation of any authorities having jurisdiction with which this publication may conflict.

API publications are published to facilitate the broad availability of proven, sound engineering and operating practices. These publications are not intended to obviate the need for applying sound engineering judgment regarding when and where these publications should be utilized. The formulation and publication of API publications is not intended in any way to inhibit anyone from using any other practices.

Any manufacturer marking equipment or materials in conformance with the marking requirements of an API standard is solely responsible for complying with all the applicable requirements of that standard. API does not represent, warrant, or guarantee that such products do in fact conform to the applicable API standard.

Classified areas may vary depending on the location, conditions, equipment, and substances involved in any given situation. Users of this Recommended Practice should consult with the appropriate authorities having jurisdiction.

Users of this Recommended Practice should not rely exclusively on the information contained in this document. Sound business, scientific, engineering, and safety judgment should be used in employing the information contained herein.

Information concerning safety and health risks and proper precautions with respect to particular materials and conditions should be obtained from the employer, the manufacturer or supplier of that material, or the material safety data sheet.

API is not undertaking to meet the duties of employers, manufacturers, or suppliers to warn and properly train and equip their employees, and others exposed, concerning health and safety risks and precautions, nor undertaking their obligations to comply with authorities having jurisdiction.

Where applicable, authorities having jurisdiction should be consulted.

Work sites and equipment operations may differ. Users are solely responsible for assessing their specific equipment and premises in determining the appropriateness of applying the Recommended Practice. At all times users should employ sound business, scientific, engineering, and judgment safety when using this Recommended Practice.

API is not undertaking to meet the duties of employers, manufacturers, or suppliers to warn and properly train and equip their employees, and others exposed, concerning health and safety risks and precautions, nor undertaking their obligations to comply with authorities having jurisdiction.

All rights reserved. No part of this work may be reproduced, translated, stored in a retrieval system, or transmitted by any means, electronic, mechanical, photocopying, recording, or otherwise, without prior written permission from the publisher. Contact the Publisher, API Publishing Services, 1220 L Street, NW, Washington, DC 20005.

## Foreword

Nothing contained in any API publication is to be construed as granting any right, by implication or otherwise, for the manufacture, sale, or use of any method, apparatus, or product covered by letters patent. Neither should anything contained in the publication be construed as insuring anyone against liability for infringement of letters patents.

Shall: As used in a standard, “shall” denotes a minimum requirement in order to conform to the specification.

Should: As used in a standard, “should” denotes a recommendation or that which is advised but not required in order to conform to the specification

This document was produced under API standardization procedures that ensure appropriate notification and participation in the developmental process and is designated as an API standard. Questions concerning the interpretation of the content of this publication or comments and questions concerning the procedures under which this publication was developed should be directed in writing to the Director of Standards, American Petroleum Institute, 1220 L Street, NW, Washington, D.C. 20005. Requests for permission to reproduce or translate all or any part of the material published herein should also be addressed to the director.

Generally, API standards are reviewed and revised, reaffirmed, or withdrawn at least every five years. A one-time extension of up to two years may be added to this review cycle. Status of the publication can be ascertained from the API Standards Department, telephone (202) 682-8000. A catalog of API publications and materials is published annually and updated quarterly by API, 1220 L Street, NW, Washington, D.C. 20005.

Suggested revisions are invited and should be submitted to the Standards Department, API, 1220 L Street, NW, Washington, D.C. 20005, [standards@api.org](mailto:standards@api.org).



## Contents

	Page
1 Scope .....	1
2 Normative References .....	1
3 Terms, Definitions, and Acronyms .....	3
3.1 Terms and Definitions .....	3
3.2 Acronyms.....	5
4 Design of Pressure Vessels and Heat Exchangers .....	5
4.1 Design and Manufacture .....	5
4.2 Coverage of Design Issues .....	6
5 Base Metal Requirements .....	6
5.1 Material Specification .....	6
5.2 Steelmaking Practice .....	7
5.3 Chemical Composition Limits .....	7
5.4 Heat Treatment .....	7
5.5 Mechanical Properties .....	8
6 Welding Consumable Requirements.....	9
6.1 Material Requirements .....	9
6.2 Mechanical Requirements .....	9
7 Welding, Heat Treatment, and Production Testing .....	9
7.1 General Welding Requirements .....	9
7.2 Welding Procedure Qualification.....	10
7.3 Preheat and Dehydrogenation Heat Treatment .....	11
7.4 Production Testing of Base Metal Welds .....	11
7.5 Weld Overlay or Integral Clad .....	12
7.6 Final PWHT .....	13
8 Nondestructive Examination (NDE).....	14
8.1 General.....	14
8.2 NDE Prior to Fabrication .....	14
8.3 NDE During Fabrication .....	15
8.4 NDE After Fabrication and Prior to Final PWHT.....	15
8.5 NDE After Final PWHT .....	15
8.6 Positive Material Identification .....	15
9 Hydrostatic Testing.....	15
10 Preparation for Shipping .....	16
11 Documentation .....	16
Bibliography.....	17
<b>Figures</b>	
1 Location of Vickers Hardness Indentations.....	11
<b>Tables</b>	
1 Base Metal ASME Specifications.....	6



## **Introduction**

This recommended practice applies to new pressure vessels in petroleum refining, petrochemical, industrial gas, and chemical facilities in which fluids are processed at temperatures in the 825 °F to 1150 °F (440 °C to 620 °C) range. It is based on decades of industry operating experience and the results of recent experimentation and testing conducted by independent manufacturers, fabricators, and users of pressure vessels for this service.

Licensors and owners of process units in which these pressure vessels are to be used may modify and/or supplement this recommended practice with additional proprietary requirements.

# Recommended Practice for Materials and Fabrication of 1¼Cr-½Mo Steel Pressure Vessels for Service above 825 °F (440 °C)

## 1 Scope

This recommended practice (RP) includes materials and fabrication requirements for new 1¼Cr-½Mo and 1Cr-½Mo steel pressure vessels, including heat exchanger shells and channels for elevated temperature service. It applies to vessels that are designed, fabricated, and documented in accordance with ASME Code Section VIII, Division 1 or Division 2 (hereafter referred to as “Code”).

This document may also be used as a resource when planning to modify existing pressure vessels.

The interior surfaces of these pressure vessels and heat exchangers (i.e. the surfaces exposed to the process) may or may not have an austenitic stainless steel (SS), ferritic SS, or nickel alloy weld overlay or cladding to provide additional corrosion resistance.

Some 1¼Cr-½Mo and 1Cr-½Mo components with thicknesses greater than 4 in. (100 mm) have been shown to have difficulty meeting the Code toughness requirements. This recommended practice is primarily intended for wall thicknesses less than 4 in. (100 mm); a preferred option for thicker components is to use 2¼Cr-1Mo alloys.

This RP is applicable to shell thicknesses greater than 1 in. (25 mm). Although outside of the scope, this document can be used as a resource for vessels down to lower shell thicknesses with changes defined by the purchaser.

This RP is intended for use for 1¼Cr-½Mo and 1Cr-½Mo equipment operating between 825 °F (440 °C) and 1150 °F (620 °C). The primary in-service materials degradation mechanism addressed by the requirements herein is low creep ductility (LCD) cracking, which can occur at these operating temperatures if not properly addressed. LCD cracking is a form of reheat cracking.

In many cases, 1¼Cr-½Mo and 1Cr-½Mo steel equipment being designed for temperatures >825 °F (>440 °C) operate with stresses below the threshold for brittle fracture [i.e. below 8 ksi (55 MPa) as reported in API 579-1/ASME FFS-1<sup>1</sup>, or below 10% of ultimate tensile strength as reported in literature].

Typical equipment covered by the scope of this RP includes catalytic reforming reactors and fluidized catalytic cracking (FCC) unit hot wall reactors. For information on 1¼Cr-½Mo and 1Cr-½Mo equipment operating at lower temperature ranges, refer to API RP 934-C. Since hydroprocessing units are typically operated at temperatures lower than 825 °F (440 °C), the guidelines in this RP (934-E) do not apply to most hydroprocessing units; instead, they are covered by RP 934-A or 934-C. Also, since coke drums typically are more susceptible to fatigue than LCD cracking, this RP excludes coke drums from the scope; they are addressed in API Technical Report 934-G.

## 2 Normative References

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

API RP 582, *Welding Guidelines for the Chemical, Oil, and Gas Industries*

ASME<sup>1</sup> *Boiler and Pressure Vessel Code, Section II-Materials—Part C-Specification for Welding Rods, Electrodes, and Filler Metals*

---

<sup>1</sup> ASME International, 3 Park Avenue, New York, New York 10016, www.asme.org.



*ASME Boiler and Pressure Vessel Code, Section V-Nondestructive Examination*

*ASME Boiler and Pressure Vessel Code, Section VIII-Rules for Construction of Pressure Vessels, Division 1*

*ASME Boiler and Pressure Vessel Code, Section VIII-Rules for Construction of Pressure Vessels, Division 2-Alternative Rules*

*ASME Boiler and Pressure Vessel Code, Section IX-Welding, Brazing, and Fusing Qualifications*

*ASME SA-20/SA-20M, Standard Specification for General Requirements for Steel Plates for Pressure Vessels*

*ASME SA-182/SA-182M, Standard Specification for Forged or Rolled Alloy and Stainless Steel Pipe Flanges, Forged Fittings, and Valves and Parts for High-Temperature Service*

*ASME SA-263, Standard Specification for Stainless Chromium Steel-Clad Plate*

*ASME SA-264, Standard Specification for Stainless Chromium-Nickel Steel-Clad Plate*

*ASME SA-265, Standard Specification for Nickel and Nickel-Base Alloy-Clad Steel Plate*

*ASME SA-335/SA-335M, Standard Specification for Seamless Ferritic Alloy-Steel Pipe for High-Temperature Service*

*ASME SA-336/SA-336M, Standard Specification for Alloy Steel Forgings for Pressure and High-Temperature Parts*

*ASME SA-369/SA-369M, Standard Specification for Carbon and Ferritic Alloy Steel Forged and Bored Pipe for High-Temperature Service*

*ASME SA-387/SA-387M, Standard Specification for Pressure Vessel Plates, Alloy Steel, Chromium-Molybdenum*

*ASME SA-530/SA-530M, Standard Specification for General Requirements for Specialized Carbon and Alloy Steel Pipe*

*ASME SA-578/SA-578M, Standard Specification for Straight-Beam Ultrasonic Examination of Rolled Steel Plates for Special Applications*

*ASNT<sup>2</sup> Recommended Practice No. SNT-TC-1A, Personnel Qualification and Certification in Nondestructive Testing*

*ASNT CP-189, Standard for Qualification and Certification of Nondestructive Testing Personnel*

*ASTM<sup>3</sup> G146, Standard Practice for Evaluation of Disbonding of Bimetallic Stainless Alloy/Steel Plate for Use in High-Pressure, High-Temperature Refinery Hydrogen Service*

*AWS<sup>4</sup> A4.2M (ISO 8249:2000 MOD), Standard Procedures for Calibrating Magnetic Instruments to Measure the Delta Ferrite Content of Austenitic and Duplex Ferritic-Austenitic Stainless Steel Weld Metal*

*AWS A4.3, Standard Methods for Determination of the Diffusible Hydrogen Content of Martensitic, Bainitic, and Ferritic Steel Weld Metal Produced by Arc Welding*

---

<sup>2</sup> American Society for Nondestructive Testing, 1711 Arlingate Lane, Columbus, Ohio 43228-0518, [www.asnt.org](http://www.asnt.org).

<sup>3</sup> ASTM International, 100 Barr Harbor Drive, West Conshohocken, Pennsylvania 19428, [www.astm.org](http://www.astm.org).

<sup>4</sup> American Welding Society, 550 NW LeJeune Road, Miami, Florida 33126, [www.aws.org](http://www.aws.org).

WRC<sup>5</sup> Bulletin 452, *Recommended Practices for Local Heating of Welds in Pressure Vessels*

WRC Bulletin 519, *Stainless Steel Weld Metal—Prediction of Ferrite Content: An Update of WRC Bulletins 318 and 342*

### 3 Terms, Definitions, and Acronyms

#### 3.1 Terms and Definitions

For the purposes of this document, the following definitions apply.

##### 3.1.1

##### **ASME Code**

ASME Boiler and Pressure Vessel Code.

##### 3.1.2

##### **final post-weld heat treatment (PWHT)**

The last PWHT after fabrication of the vessel and prior to affixing the name plate and placing the vessel in service.

##### 3.1.3

##### **fine grain practice**

A steelmaking practice where aluminum or other elements are added to steel to provide resistance to grain growth during heat treatments.

NOTE The steps and/or testing to achieve fine grain practice are defined in the ASME specifications for materials (e.g. ASME SA-20/SA-20M, Paragraph 8).

##### 3.1.4

##### **hot forming**

Mechanical forming operation producing permanent deformation, performed with the rolled or forged/rolled plate heated to above the temperature required to produce grain refinement or recrystallization.

##### 3.1.5

##### **Larson-Miller parameter (LMP)**

Parametric relationship proportional to the heat treatment temperature(s) and duration(s). LMP can be used to assess the effect of individual or multiple heat treatment(s) on a specific material property, such as strength or toughness. LMP is employed to evaluate cumulative effects from exposures to varying temperatures during fabrication, including tempering and PWHT.

$$LMP = T \times (20 + \log t)$$

$T$  is the temperature in Kelvin

$t$  is time in hours

NOTE Hollomon-Jaffe parameters can be used in place of LMP parameters, as they use the same concept and formula structure, but have different constants. LMP is also referred to as the "tempering parameter."

##### 3.1.6

##### **low creep ductility (LCD) cracking**

A form of reheat cracking occurring due to long-term exposure to temperatures >825 °F (440 °C) for 1<sup>1</sup>/<sub>4</sub>Cr-1<sup>1</sup>/<sub>2</sub>Mo and 1Cr-1<sup>1</sup>/<sub>2</sub>Mo steels. It involves creep cracking of welds or weld heat-affected zones due to carbide precipitation

---

<sup>5</sup> The Welding Research Council, 3 Park Avenue, 27th Floor, New York, New York 10016-5902, [www.forengineers.org](http://www.forengineers.org).

and diffusion of certain elements (As, Cu, P, B, Sb, Sn, Nb, V, Ti, etc.) to grain boundaries. These precipitates result in loss of creep ductility, and significant lowering of the expected creep life.

NOTE This phenomenon is also called “creep embrittlement cracking” in older publications.

### 3.1.7

#### **master plate**

The term used by ASME SA-20/SA-20M to describe starting plates that are subdivided into multiple plates.

### 3.1.8

#### **maximum PWHT**

Specified heat treatment (aggregate temperature and time) of test specimens to simulate the maximum heat-treatment exposures on the vessel. The test coupons (initially with the same austenitizing and tempering heat treatment as the as-supplied material) are heat treated at a temperature and time that simulates all fabrication heat treatments above 900 °F (482 °C). This includes the intermediate stress relief (ISR), all PWHT cycles, a PWHT cycle for possible shop repairs, and a minimum of one extra PWHT for possible future use by the purchaser. Typically, the ISR and PWHT cycles are aggregated into one single equivalent heat treatment, as discussed in the note below. Dehydrogenation heat treatments (DHT) do not need to be included, as they are at too low of a temperature to affect material properties.

NOTE To determine the equivalent time at one temperature (within the PWHT range) of heat steps outside the PWHT range, the Larson-Miller Parameter formula may be used; results are to be agreed upon by the purchaser and fabricator. At the time of any future repairs, it is the owner’s responsibility to determine any changes in strength and toughness properties of the material that may have occurred from high-temperature service. The results achieved by the maximum PWHT testing may not be representative of the actual mechanical properties after exposure to service temperature.

### 3.1.9

#### **minimum PWHT**

Specified heat treatment (aggregate temperature and time) of test specimens to simulate the minimum heat-treatment exposures on the vessel. The test coupons (initially with the same austenitizing and tempering heat treatment as the as-supplied material) are heat treated at a temperature and time that simulates the minimum of all fabrication heat treatments above 900 °F (482 °C). This typically includes the ISR, if any, and one PWHT cycle. Typically, the ISR and PWHT cycles are aggregated into one single equivalent heat treatment, as discussed in the note below.

NOTE To determine the equivalent time at one temperature (within the PWHT range) of heat steps outside the PWHT range, the Larson-Miller Parameter formula (or Hollomon-Jaffe Parameter) may be used; results are to be agreed upon by the purchaser and fabricator.

### 3.1.10

#### **purchaser**

The firm or organization that has entered into the purchase order with the manufacturer, or their designated representative.

### 3.1.11

#### **reheat cracking**

Creep cracking of welds or weld heat-affected zones after a fabrication heat-treatment step, such as PWHT, or after long-term service at high temperatures. However, in this document, the latter is referred to as low creep ductility cracking. Both forms are due to diffusion of certain elements (P, As, Cu, Sb, Sn, B) to grain boundaries and precipitation of carbides of Mo, Nb, V, Ti in grains. At PWHT temperatures, precipitation of fine carbides strengthens the intragranular matrix, resulting in the strength of the grain exceeding that of the grain boundaries. Additionally, diffusion of tramp elements to the grain boundaries promotes low creep ductility, and can crack at the high temperatures due to the welding residual stresses. Heavier thickness welds are more susceptible, as they develop larger thermal stresses and require longer times to achieve stress relief. This phenomenon is also called “stress relaxation cracking” in other publications.

### 3.1.12

#### temper embrittlement

The “reversible” reduction in toughness due to a metallurgical change (primarily impurity segregation at grain boundaries) that can occur in some low-alloy steels as a result of long-term exposure in the temperature range of about 650 °F to 1070 °F (343 °C to 577 °C). This change causes an upward shift in the ductile-to-brittle transition temperature as measured by Charpy impact testing. Although the loss of toughness is not evident at operating temperature, equipment that is temper embrittled may be susceptible to brittle fracture during start-up, shutdown, or hydrotesting after weld repair. 1<sup>1</sup>/<sub>4</sub>Cr-1<sup>1</sup>/<sub>2</sub>Mo and 1Cr-1<sup>1</sup>/<sub>2</sub>Mo steels are considered to be less susceptible and to have less of a shift than 2<sup>1</sup>/<sub>4</sub>Cr-1Mo alloys.

## 3.2 Acronyms

For the purposes of this document, the following acronyms apply.

CVN	Charpy V-notch
DHT	dehydrogenation heat treatment
FN	ferrite number
HAZ	heat-affected zone
HBW	Brinell hardness with tungsten carbide indenter
HV	Vickers hardness
LCD	low creep ductility
LMP	Larson-Miller parameter
MDMT	minimum design metal temperature
MT	magnetic particle testing
MTR	material test report
NDE	nondestructive examination
PQR	procedure qualification record
PT	penetrant testing
PWHT	post-weld heat treatment
RT	radiographic testing
SS	stainless steel
UT	ultrasonic testing
WPS	welding procedure specification

## 4 Design of Pressure Vessels and Heat Exchangers

### 4.1 Design and Manufacture

Design and manufacture shall conform to the ASME *Boiler and Pressure Vessel Code*, Section VIII, Division 1 or Division 2. The latest edition of the Code, including addenda effective through the date of the purchase agreement, shall be used.

## 4.2 Coverage of Design Issues

Design issues are typically covered by a manufacturer's design report that shows compliance of the design with the user's design document; ASME Code strength calculations, drawings, and local stress analysis for extra loads; and special design requirements, if required.

This recommended practice is not intended to cover design issues, other than those below.

- a) The design thickness (T) shall not include any allowance for extra thickness provided either as corrosion allowance or as a corrosion-resistant liner, such as weld overlay or cladding.
- b) Weld seam layouts shall provide that all welds are accessible for NDE, such as RT, UT, MT, and PT, both during fabrication and in service. The use of external attachments that cover weld seams should be avoided, and require purchaser approval.
- c) Nozzle necks should have transition to the vessel body as shown in Table 4.2.13 of the ASME Code, Section VIII, Division 2, or be fabricated in accordance with Table 4.2.10, Details 3 through 6 of the ASME Code, Section VIII, Division 2, with integral reinforcement.
- d) Where possible, nozzle welds should be located without intersecting of circumferential or longitudinal welds. Purchaser approval and additional NDE shall be required for any cases of intersection.
- e) Class 1 or 2 plates and Grade 1, 2, or 3 forgings, pipe fittings, and flanges and Grade P11 and FP11 pipe may be used for the pressure boundary as indicated in Table 1. Regardless of the class of material used, the ASME Code design allowable stresses shall be based on Class 1 materials. It is acceptable per Code to arbitrarily use lower design allowable stresses. This only has an effect for design temperatures between 850 °F (455 °C) and 900 °F (480 °C), because, at design temperatures  $\geq$  900 °F (480 °C), the Code design allowable stresses are the same for Class 1 and 2.

## 5 Base Metal Requirements

### 5.1 Material Specification

**5.1.1** Pressure boundary base metals shall be in accordance with the applicable ASME specifications indicated in Table 1. Tubing is outside the scope of this document.

**Table 1—Base Metal ASME Specifications**

Steel	Plate	Forgings	Pipe	Pipe Fittings and Flanges
1¼Cr-½Mo	SA-387 Gr. 11, Cl. 1 or Cl. 2	SA-182 Gr. F11, Cl. 1, 2, or 3 SA-336 Gr. F11, Cl. 1, 2, or 3	SA-335 Gr. P11 SA-369 Gr. FP 11	SA-182 Gr. F11, Cl. 1, 2 or 3 SA-234 Gr. WP11, Cl. 1, 2 or 3
1Cr-½Mo	SA-387 Gr. 12, Cl. 1 or Cl. 2	SA-182 Gr. F12, Cl. 1 or 2 SA-336 Gr. F12 Cl. 1 or 2	SA-335 Gr. P12 SA-369 Gr. FP12	SA-182 Gr. F12, Cl. 1, 2, or 3 SA-234 Gr. WP12, Cl. 1 or 2
NOTE 1 If higher PWHT temperatures are used as discussed in Paragraph 7.6.1, it may be difficult to achieve Class 2 or 3 mechanical properties.				
NOTE 2 All designs shall be based on Class 1 design allowable stresses per Paragraph 4.3.e.				

**5.1.2** External attachments (such as skirts, lugs, clips, etc.) welded directly to the pressure boundary shall be of the same material grade as the pressure boundary material.

**5.1.3** Nozzles shall be manufactured from forgings.

## 5.2 Steelmaking Practice

In addition to the steelmaking practice outlined in the applicable specifications, steel plates and heavy forgings made to SA-336/SA-336M shall be vacuum degassed. For pipes, pipe fittings, and pipe flanges made to SA-182/SA-182M, vacuum degassing is not mandatory.

## 5.3 Chemical Composition Limits

For 1<sup>1</sup>/<sub>4</sub>Cr-<sup>1</sup>/<sub>2</sub>Mo and 1Cr-<sup>1</sup>/<sub>2</sub>Mo steels, all plate, piping, and forging materials should be made to fine grain practice per ASME SA-20/SA-20M (no grain size measurement is required if the chemical analysis requirements of SA-20/SA-20M 8.3.2 are met). The steel shall meet the following additional chemical analysis by heat analysis:

$$\bar{X} \leq 15 \text{ ppm}$$

$$\text{Where } \bar{X} = (10P + 5Sb + 4Sn + As)/100 \quad [\text{with } P, Sb, Sn, \text{ and } As \text{ in ppm}]$$

$$C = 0.15 \text{ wt. \%, maximum}$$

$$P = 0.010 \text{ wt. \%, maximum}$$

$$S = 0.007 \text{ wt. \%, maximum}$$

$$Cu = 0.20 \text{ wt. \%, maximum}$$

$$Ni = 0.30 \text{ wt. \%, maximum}$$

$$Nb = 0.006 \text{ wt. \%, maximum}$$

$$V = 0.025 \text{ wt. \%, maximum}$$

$$Ti = 0.02 \text{ wt. \%, maximum}$$

**NOTE** While the J-factor is used to mitigate temper embrittlement in 2<sup>1</sup>/<sub>4</sub>Cr-1Mo steels, it is not applicable to 1<sup>1</sup>/<sub>4</sub>Cr-<sup>1</sup>/<sub>2</sub>Mo and 1Cr-<sup>1</sup>/<sub>2</sub>Mo steels, and an X-bar limit has been adopted as a means of restricting the concentration of elements that contribute to temper embrittlement, reheat cracking, and LCD cracking. The chemistry restrictions described above, along with other aspects of this RP, are designed to provide the steel with resistance to reheat and LCD cracking, balanced with the other desired properties. API Publication 938-A was used as a basis for these requirements, and the optimum limits have been compiled. The MPC-05 and MPC-07 formulas discussed in Publication 938-A are too complicated for steelmakers to develop strategies to consistently meet, and hence, it would be extremely impractical to add to purchasing requirements.

## 5.4 Heat Treatment

Pressure-boundary components, regardless of product form, shall be either:

- annealed;
- normalized and tempered (N&T); or
- quenched and tempered [Q&T or normalized with accelerated cooling and tempered (N+Ac+T)] to meet the required mechanical properties.

For thicknesses >2 in. (50 mm), Q&T or N+Ac+T may be required to meet fracture-toughness specifications. Tempering temperature may be below, at, or above PWHT temperature.

**NOTE** Plate and forged materials manufacturers are responsible for determining the tempering temperatures required to meet the specified material properties, considering all heat-treatment requirements (i.e. including the minimum and maximum PWHT as defined in 3.1.8 and 3.1.9). The cumulative effects of the various heat treatments shall be evaluated by using the equivalent LMP approach as required for mechanical property testing in 5.5.2.a, 5.5.3, and 6.2.

## 5.5 Mechanical Properties

### 5.5.1 Location of Tensile Test Specimens

Test specimens for establishing the tensile properties shall be removed from the following locations:

- a) Plate—from each master plate, at the  $\frac{1}{2}T$  location ( $\frac{1}{2}T$  is acceptable per Code by specifying SA-387 Supplementary Requirement S53). Specimens shall be oriented transverse to the rolling direction in accordance with SA-20/SA-20M.

**NOTE** If multiple plates are cut from one master plate, only one set of specimens from the master plate (i.e. one set from each heat and heat-treatment batch) is required.

- b) Forging—from each heat, at  $\frac{1}{2}T$  of the prolongation or of a separate test block (sample distance from side edges shall be per Code). Specimens shall be oriented transverse to the major working direction in accordance with ASME SA-182/SA-182M or ASME SA-336/SA-336M. A separate test block, if used, shall be made from the same heat, and shall receive substantially the same reduction and type of hot working as the production forgings that it represents, and shall be of the same nominal thickness as the production forgings. The separate test forging shall be heat treated in the same furnace charge and under the same conditions as the production forgings.
- c) Pipe—from each heat and lot of pipe, at  $\frac{1}{2}T$ . Specimens shall be oriented transverse to the major working direction in accordance with ASME SA-530/530M.

### 5.5.2 Tensile Test Requirements

Tensile testing of plates and forging materials shall comply with the applicable code(s) and the following additional requirements:

- Test coupons for N&T, Q&T, and N+Ac+T steels shall be heat treated to represent the maximum PWHT as defined in 3.1.8, in addition to any requirements of the applicable code. Coupons from annealed steels can be tested at minimum or maximum PWHT.
- Tensile values at room temperature shall meet the requirements of the applicable code(s).

### 5.5.3 Impact Testing Requirements

Charpy V-notch (CVN) impact testing shall be performed for all  $1\frac{1}{4}Cr\text{-}\frac{1}{2}Mo$  and  $1Cr\text{-}\frac{1}{2}Mo$  steel material used for pressure-containing components. Impact testing is required for all material thickness and minimum design metal temperature (MDMT) combinations, and shall be done on test coupons heat treated to represent the maximum PWHT as defined in 3.1.8, in addition to any requirements of the applicable code. One exception is that coupons from annealed steels can be tested at minimum or maximum PWHT.

CVN impact tests shall be performed at the vessel MDMT or lower, and shall comply with the testing procedures and criteria given in the applicable code(s). Test coupons shall be from the  $\frac{1}{2}T$  location.

## 6 Welding Consumable Requirements

### 6.1 Material Requirements

**6.1.1** The deposited weld metal, from each lot or batch of welding electrodes and each heat of filler wires, and each combination of filler wire and flux, shall match the nominal chemical composition of the base metal to be welded.

**6.1.2** The following chemical composition limits shall be controlled to improve resistance to temper embrittlement, reheat cracking, and low creep ductility cracking. The chemical composition restriction applies to the heat analysis.

$$X\text{-bar} = (10P + 5Sb + 4Sn + As) / 100 \leq 15 \text{ ppm}$$

Where P, Sb, Sn, and As are in ppm

C = 0.15 wt.% maximum

Cu = 0.20 wt.% maximum

Ni = 0.30 wt.% maximum

**6.1.3** Low hydrogen welding electrodes, having a maximum diffusible hydrogen of 8 mL per 100 g of weld metal per AWS A4.3, shall be used. Welding consumables shall be baked, stored, and used in accordance with manufacturer's instructions (for holding in electrode oven, length of time out of oven, use of electrically-heated quivers, etc.).

### 6.2 Mechanical Requirements

#### 6.2.1 Tensile Properties

Tensile properties of deposited weld metal shall meet that of the base metal in accordance with 5.5.2.

#### 6.2.2 Impact Properties

Whenever CVN impact testing is required for base materials per 5.5.3, each lot of electrodes, heat of filler wire, and combination of lot of flux and heat of wire, shall be screened by impact testing of weld deposit prior to the start of fabrication. Impact testing shall be done on test coupons heat treated to represent the minimum and maximum PWHT as defined in 3.1.8 and 3.1.9, in addition to any requirements of the applicable code.

CVN impact tests shall be performed at the vessel MDMT or lower, and shall comply with the testing procedures and criteria required for the base metals.

## 7 Welding, Heat Treatment, and Production Testing

### 7.1 General Welding Requirements

**7.1.1** Base metal surfaces prior to welding or applying weld overlay shall consist of clean metal prepared by machining, grinding, or blast cleaning.

**7.1.2** Welded joints, including non-pressure attachments to the vessel body, shall:

- a) be full-penetration joints, except for external attachments greater than 19 mm (<sup>3</sup>/<sub>4</sub> in.) thick when allowed by Code and approved by the purchaser. If approved, the gap between the attachment and shell or head shall be vented;



- b) be located so that full ultrasonic examination of welds can be made after fabrication and after the equipment has been in service. In cases where this is not practical, the manufacturer shall propose alternate NDE methods to verify weld quality for purchaser approval;
- c) be made sufficiently smooth to facilitate nondestructive examination (MT, PT, UT, or RT), as applicable.

**7.1.3** Welding shall be completed prior to final PWHT, except for welding of internal attachments to the corrosion-resistant weld overlay or cladding, when permitted. For these attachment welds, a PQR and/or mockup test shall be performed to verify that this does not produce a HAZ in the base metal, unless waived by the purchaser.

**7.1.4** Shop weld repairs to base metal, weld joints, and weld overlay shall be performed using a repair welding procedure qualified in accordance with 7.2, and shall meet all the same requirements as the normal fabrication welds.

## **7.2 Welding Procedure Qualification**

**7.2.1** Welding procedures shall be qualified in accordance with ASME *Code* Section IX, with the following additional requirements.

**7.2.2** Base metal for welding procedure qualification tests shall be made from the same ASME base metal specification (same P-number and Group number) and be similar in chemical composition as specified for the vessel, but either plate or forging may be used. The welding consumable combination (electrodes, wire, and flux—whichever are applicable) shall be of the same type and similar in chemical composition as those to be used in production welding.

**7.2.3** Vickers hardness traverses of the weld joint shall be made on a weld sample in the minimum PWHT condition. These hardness traverses shall be performed at locations similar to those shown in Figure 1. If previously qualified WPS/PQRs are proposed, the purchaser shall decide if the hardness test locations are sufficient. The hardness shall not exceed 248 HV10.

**7.2.4** Tensile testing, transverse to the weld, shall be performed on a weld joint of the heat-treated test plate in the maximum PWHT condition, and shall meet the ambient temperature ultimate tensile strength specified for the base metal in 5.5.2. One exception is that coupons from annealed steels can be tested at minimum or maximum PWHT.

**7.2.5** Charpy V-notch impact testing shall be performed on weld metal and HAZ of the heat-treated test plate in the minimum and maximum PWHT conditions. These impact tests shall be performed for each welding procedure and shall meet the impact test temperature and acceptance requirements in 5.5.3.

**7.2.6** WPSs/PQRs shall comply with ASME Section IX and this RP, and shall be submitted to the purchaser for review and acceptance prior to fabrication.

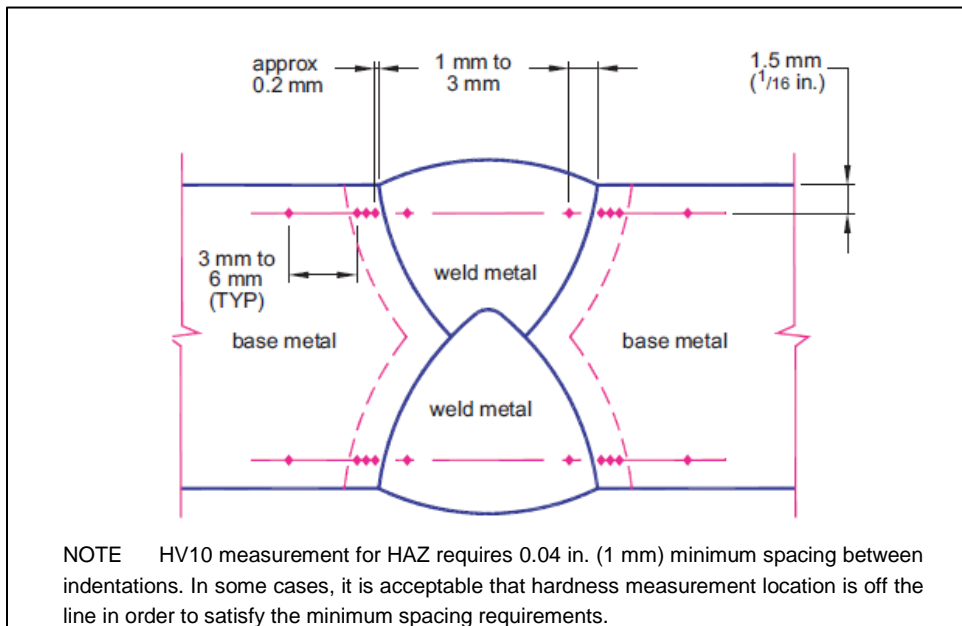


Figure 1—Location of Vickers Hardness Indentations

## 7.3 Preheat and Dehydrogenation Heat Treatment

### 7.3.1 Preheat During Fabrication Steps Other than Welding

Base metals shall be heated to a minimum of 300 °F (150 °C) during all rolling, forming, pressing, thermal cutting, and gouging operations. Preheating for rolling of plates less than 2 in. (50 mm) thick can be waived for ambient temperature >50 °F (10 °C) with approval of the purchaser.

### 7.3.2 Preheat During Welding

Base metals shall be heated to a minimum of 300 °F (150 °C) during all welding operations [except as modified for weld overlay (see 7.5.4)]. For butt welding and attachment welding, this preheat temperature shall be maintained through the entire plate thickness for a distance of at least one plate thickness on either side of the weld, but need not extend more than 4 in. (100 mm) in any direction from the edges to be welded.

During welding, the preheat temperature shall be maintained until PWHT or dehydrogenation heat treatment (DHT) is performed in accordance with 7.3.3.

### 7.3.3 Dehydrogenation Heat Treatment (DHT)

The DHT shall be performed at a minimum metal temperature of 570 °F (300 °C) for a minimum duration of one hour. In lieu of a DHT for tack welds, preheat shall be held for a minimum of 15 minutes after completion of tack weld.

## 7.4 Production Testing of Base Metal Welds

### 7.4.1 Chemical Composition of Production Welds

7.4.1.1 The chemical composition of weld deposits representing each different welding procedure shall be checked by either laboratory chemical analysis or by using a portable analyzer of equivalent accuracy and precision.

7.4.1.2 The chromium and molybdenum content of weld deposits shall be within the ranges specified in ASME Code Section II, Part C, for the specified electrodes.

## 7.4.2 Hardness of Weld Deposit and Adjacent Base Metal (Heat -affected Zone)

**7.4.2.1** After final PWHT (see 7.6), hardness testing shall be performed for each pressure-retaining weld by using a portable hardness tester.

**7.4.2.2** Reported test results at each hardness test location shall be the average of three impressions at each test location. The test locations shall include weld metal and, if required by the purchaser, base metals adjacent to the fusion line on both sides.

**7.4.2.3** Average hardness results at each test location shall not exceed 225 HBW. Hardness testing methods that give results in other units can have the results converted to HBW.

**7.4.2.4** Hardness tests shall be performed on each 10-foot (3-meter) length of weld, or fraction thereof. This testing shall be performed on the side exposed to the process environment when accessible. This requirement does not apply to weld overlays or welds that are covered with weld overlay on the side exposed to the process.

NOTE HAZ hardness tests on vessel production weldments may actually be an average of the HAZ, weld deposit, and base metal hardnesses, as the test indentation is generally larger than the HAZ width.

## 7.4.3 Weld Impact Tests

Production test plates are only required if required by Code.

## 7.5 Weld Overlay or Integral Clad

To provide a corrosion layer on the internal surface of the equipment, one or more of the following options can be used:

- austenitic SS weld overlay,
- nickel alloy weld overlay,
- austenitic SS integral cladding (refer to ASME SA-264),
- ferritic or martensitic SS integral cladding (refer to ASME SA-263), and/or
- nickel alloy integral cladding (refer to ASME SA-265)

The following special requirements shall apply.

### 7.5.1 Material Requirements

The ferrite content of austenitic stainless steel weld overlay shall be between 3 FN and 10 FN, as determined in accordance with WRC Bulletin 519, prior to any PWHT, but the ferrite content for Type 347 SS shall be between 5 and 10 FN (in accordance with API RP 582).

### 7.5.2 Disbonding Tests

Experience indicates that the risk of disbonding is low at the thicknesses and hydrogen charging levels at which 1¼Cr-½Mo and 1Cr-½Mo steels are used; hence, testing is not required by this RP. If testing is considered, API RP 934-A can be consulted as a resource, and the purchaser shall define testing requirements and acceptance criteria (refer to ASTM G146).

### 7.5.3 Weld Overlay Procedure Qualification

**7.5.3.1** The selected weld overlay process and the number of layers shall be qualified in accordance with ASME Section IX.

**7.5.3.2** Procedure qualification tests shall be made on base metal of the same ASME specification as specified for the vessel, but either plate or forging may be used. Thickness of the test specimen shall not be less than one half the thickness of the equipment base metal or 2 in. (50 mm), whichever is less. The welding electrode, wire/strip, and flux used for the weld overlay procedure qualification shall be the same type to be used in production.

**7.5.3.3** The qualification test plates shall be subjected to the maximum PWHT condition. One exception is that coupons from annealed steels can be tested at minimum or maximum PWHT.

**7.5.3.4** Weld overlay chemical composition shall be determined for each overlay WPS at an agreed-upon depth (or distance from fusion line) and at the final surface [see ASME IX, Figure QW-462.5(a)]. Weld composition at the agreed-upon depth shall meet the filler-metal specification or other requirements as defined by the purchaser.

### 7.5.4 Preheat and Heat Treatments During Weld Overlay

For weld overlay with austenitic stainless steel or nickel-based alloy, the base metal shall be preheated to and maintained at or above 200 °F (94 °C) for the first layer of weld overlay. No preheating is required for the second and subsequent layers of weld overlay.

### 7.5.5 Production Testing of Weld Overlay

#### 7.5.5.1 Chemical Composition of Weld Overlay

The chemical composition of the weld overlay shall be checked by laboratory chemical analysis of a sample taken at minimum specified thickness below the surface. This composition shall meet the specified composition of the overlay material (C, Cr, Ni, Mo, and Nb, as applicable). At least one analysis for each WPS, and for each shell ring and head, and one for each manual welding process for nozzles, shall be required. Use of Positive Materials Identification (PMI) testers at the required thickness, may also be used if approved by the purchaser.

#### 7.5.5.2 Ferrite Content of Austenitic Stainless Weld Overlay

**7.5.5.2.1** A magnetic instrument calibrated to AWS A4.2M shall be used to check the ferrite content of the production weld overlay prior to any PWHT.

**7.5.5.2.2** Calibration for the steel backing material in accordance with AWS A4.2M, Appendix A7, Paragraph A7.1, may be used.

**7.5.5.2.3** A minimum of six ferrite readings shall be taken on the surface at each of the following locations:

- a) at least 10 locations, selected at random, shall be checked for each shell ring and head;
- b) two locations for each nozzle overlay (one at each end); and
- c) one location on cladding or overlay restoration of each category A, B, and D weld joint, if applicable.

**7.5.5.2.4** The value of all ferrite readings at each location shall meet the requirements of 7.5.1.

### 7.6 Final PWHT

**7.6.1** PWHT shall comply with the minimum requirements of the applicable code, except that 1 $\frac{1}{4}$ Cr-1 $\frac{1}{2}$ Mo and 1Cr-1 $\frac{1}{2}$ Mo weld joints shall be PWHT at 1225 °F (663 °C) to 1275 °F (690 °C). The use of PWHT temperatures higher than the Code minimum requirements helps to prevent reheat and LCD cracking. PWHT at 1275 °F (690 °C) to 1325 °F (720 °C) can be considered when the primary failure mechanism expected for the service is

creep. However, the use of PWHT 1275 °F (690 °C) to 1325 °F (720 °C) temperatures may result in lower steel tensile strength and impact toughness (the testing requirements in this Recommended Practice and within the Code will confirm whether the base materials and weld deposit have met the required mechanical properties). Designers and fabricators are cautioned to consider PWHT temperatures and the possible difficulties in meeting material properties when they are selecting between Class 1 and Class 2 materials (also note that all designs, with either Class 1 or 2 materials, shall be based on Class 1 design allowable stresses per Paragraph 4.3.e).

**7.6.2** The fabricated vessel shall be PWHT as a whole in an enclosed furnace whenever possible. When vessel size does not allow PWHT as a whole in a furnace, PWHT may be performed sectionally according to the ASME Code.

**7.6.3** PWHT temperature (during heating, holding, and cooling) shall be strictly controlled, measuring both the vessel skin and furnace temperatures using thermocouples, including any portion of the vessel outside of the furnace. Any section of the vessel outside the furnace shall be insulated such that the temperature gradient is not harmful. Thermocouple arrangements shall be established for each heat treatment. The skin temperature shall be measured and controlled on the inside and outside of the vessel. Local PWHT procedures shall meet the soak, heating, and gradient control bandwidths, and thermocouple placements recommended by WRC Bulletin 452.

**7.6.4** Continuous time-temperature records of all PWHT operations shall be documented to meet the requirements of the ASME Code.

## **8 Nondestructive Examination (NDE)**

### **8.1 General**

**8.1.1** NDE personnel shall be qualified in accordance with ASNT Recommended Practice SNT-TC-1A or ASNT CP-189 or other agencies with purchaser approval. For ASME Section VIII, Division 2, vessels, NDE personnel shall be qualified per Paragraph 7.3 of Section VIII, Division 2. Personnel interpreting and reporting results should also be qualified to the same practice.,

**8.1.2** Where references to ASME Section VIII, Division 2 inspection requirements are listed, they shall be applied to ASME Section VIII, Division 1 or Division 2, vessels and heat exchangers.

### **8.2 NDE Prior to Fabrication**

#### **8.2.1 Ultrasonic Testing (UT)**

**8.2.1.1** Bare and clad base metal plates shall be ultrasonically examined with 100% scanning in accordance with ASME Section V and SA-578/SA-578M, Level C, Supplementary Requirement S1, before forming.

**8.2.1.2** Forgings for shell rings, nozzles, and manways shall be ultrasonically examined with 100% scanning in accordance with Paragraph 3.3.4 of ASME Section VIII, Division 2.

#### **8.2.2 Magnetic Particle Testing (MT) or Dye Penetrant Testing (PT)**

**8.2.2.1** Entire surfaces of forgings, including welding edges, shall be examined by MT in accordance with Paragraph 7.5.6 or by PT in accordance with Paragraph 7.5.7 of ASME Section VIII, Division 2. Examination should be after finish machining, but before welding.

**8.2.2.2** For formed plates to be welded for shell rings and heads, welding edges shall be examined by MT or PT.

**8.2.2.3** Where nozzle welds intersect circumferential and longitudinal welds (if approved per Paragraphs 4.3.d and 7.1.2.b), weld preparation surfaces (beveled edges) shall receive PT or MT inspection.

### 8.3 NDE During Fabrication

**8.3.1** MT shall be performed after completion of welds, including pressure-retaining base metal welds, weld build-up deposits, root passes, and attachment welds. MT shall also be performed after any gouging or grinding operation, including back gouging of root passes. MT shall be in accordance with Paragraph 7.5.6 of ASME Section VIII, Division 2.

**8.3.2** Temporary attachments should be minimized. Areas where temporary attachments have been removed shall be examined by MT or PT in accordance with Paragraph 7.5.6 or Paragraph 7.5.7 of ASME Section VIII, Division 2, as applicable.

### 8.4 NDE After Fabrication and Prior to Final PWHT

#### 8.4.1 Base Metal Welds

**8.4.1.1** Pressure-retaining butt welds and vessel-to-support skirt welds shall be fully examined by RT in accordance with Paragraph 7.5.3 of ASME Section VIII, Division 2, or UW-51 of ASME Section VIII, Division 1, before final PWHT, as applicable.

**8.4.1.2** UT may be applicable in lieu of RT when the UT procedure fulfills the requirements of Paragraph 7.5.5 of ASME Section VIII, Division 2.

**8.4.1.3** When RT is not practical for nozzle and skirt attachment welds, UT may be applied in lieu of RT.

#### 8.4.2 Weld Overlay

Spot UT—four strips approximately 3.2 in. (80 mm) wide along the full length of the vessel shell and one (1) strip approximately 3.2 in. (80 mm) wide across each head—shall be performed on weld overlay. UT shall be in accordance with ASME SA-578, Level C.

### 8.5 NDE After Final PWHT

#### 8.5.1 Base Metal Welds

**8.5.1.1** Pressure-retaining base metal welds, including nozzles, shall be fully examined by UT in accordance with Paragraph 7.5.4 of ASME Section VIII, Division 2.

**8.5.1.2** Accessible welds shall be examined by MT. An AC yoke method shall be used to prevent arc strikes. PT may be used instead of MT whenever MT is impractical.

**8.5.1.3** Internal weld surfaces (groove and fillet) on unclad or non-overlaid pressure-containing parts in services with >50 psia (3.45 bara) hydrogen partial pressure shall receive 100% MT inspection.

#### 8.5.2 Weld Overlay

Entire surfaces of stainless steel and nickel-based weld overlay, and attachments to the overlay, shall be examined by PT in accordance with Paragraph 7.5.7 of ASME Section VIII, Division 2.

### 8.6 Positive Material Identification

PMI shall be performed in accordance with the the purchaser's PMI specification.

## 9 Hydrostatic Testing

Pressure-retaining welded joints shall be free from any scale and other foreign matter before testing. All dirt, scale, sand, and other foreign material shall be removed from the vessel.

Test water shall not contain more than 50 ppm chlorides.

During the hydrostatic testing, the vessel metal temperature shall be at least 30 °F (17 °C) above the MDMT, or 60 °F (15 °C), whichever is warmer.

The vessel shall be drained and thoroughly dried immediately after testing.

## 10 Preparation for Shipping

Immediately after completion of final examination of the vessel, the interior of the vessel shall be cleaned and dried. Heat drying and/or other evaporative means shall not be used due to possible chloride contamination of stainless overlay or clad vessels.

All openings shall be sealed with a steel cover and gasket, and the vessel shall be filled with a minimum 5 psig (34.5 kPa) of dry nitrogen gas or use a desiccant system. If nitrogen is used, the nitrogen pressure shall be maintained during transportation, erection, and pre-commissioning. A non-removable tag shall be attached, with a warning stating that the vessel is filled with nitrogen.

For preservation during transportation, exposed machined surfaces, such as flange faces, shall be protected by applying suitable grease, rust preventative compound, or coating.

## 11 Documentation

The following documentation for all pressure-retaining parts, including welding consumables, shall be completed prior to the start of fabrication and shall be available for examination by the purchaser at the time of inspection:

- a) MTRs showing all chemical composition and mechanical test results for base metal, weld metal, and overlay material;
- b) X-bar results for base metal and Cr-Mo weld metal;
- c) welding procedure specifications with applicable procedure qualification records.

The above documentation, along with the following additional reports, shall be submitted to the purchaser at the completion of the project:

- a) heat-treatment data showing ramp-up, hold time, and temperature for PWHT and DHT;
- b) PMI report;
- c) production test results (if required by Code).





## Bibliography

- [1] API 579-1/ASME FFS-1, *Fitness-For-Service*
- [2] API RP 934-A, *Materials and Fabrication of 2¼Cr-1Mo, 2¼Cr-1Mo-¼V, 3Cr-1Mo, and 3Cr-1Mo-¼V Steel Heavy Wall Pressure Vessels for High-Temperature, High-Pressure Hydrogen Service*
- [3] API RP 934-C, *Materials and Fabrication of 1¼Cr-½Mo Steel Heavy Wall Pressure Vessels for High-pressure Hydrogen Service Operating at or Below 825 °F (441 °C)*
- [4] API TR 934-D, *Materials and Fabrication Issues of 1¼Cr-½Mo and 1Cr-½Mo Steel Pressure Vessels*
- [5] API TR 934-G, *Design, Fabrication, Operational Effects, Inspection, Assessment, and Repair of Coke Drums and Peripheral Components in Delayed Coking Units*
- [6] API Publication 938-A, *An Experimental Study of Causes and Repair of Cracking of 1¼Cr-½Mo Steel Equipment*
- [7] ASME<sup>6</sup> *Boiler and Pressure Vessel Code, Section II-Materials, Part A—Ferrous Material Specifications, and Part D—Properties*

---

<sup>6</sup> ASME International, 3 Park Avenue, New York, New York 10016, [www.asme.org](http://www.asme.org).





AMERICAN PETROLEUM INSTITUTE

1220 L Street, NW  
Washington, DC 20005-4070  
USA

202-682-8000

**Additional copies are available online at [www.api.org/pubs](http://www.api.org/pubs)**

Phone Orders: 1-800-854-7179 (Toll-free in the U.S. and Canada)  
303-397-7956 (Local and International)  
Fax Orders: 303-397-2740

Information about API publications, programs and services is available  
on the web at [www.api.org](http://www.api.org).

**Product No. C934E02**